

NUMERICAL SIMULATION OF THE KINETICS OF  
THE DENSE GAS BREAKDOWN BY THE LASER  
RADIATION NEAR A METAL SURFACE

N.N. Rykalin, V.I. Mazhukin,  
A.A. Uglov, B.N. Chetverushkin  
Keldysh Institute of Applied Mathematics,  
Academy of Sciences, Moscow, USSR

ABSTRACT

The optical breakdown of nitrogen investigated near a metallic target under the nitrogen pressure of 10 to 200 atm and the threshold values of the laser radiation intensity. The basic collisional gas reactions are analyzed and their contribution to the breakdown kinetics is estimated. The numerical results are compared with experiment.






I. INTRODUCTION

The interaction of the laser radiation of low density with metals when the ambient pressure is high (about 100 atm) is characterized by some peculiarities [1]. The laser radiation ( $\lambda = 1.06 \mu\text{m}$ ,  $G = (0.5-1) \times 10^7 \text{ w/cm}^2$ ,  $\tau = (0.5-1) \times 10^{-7} \text{ sec}$  at the laser operation in the free generation mode) focused onto the metallic surface stimulates the formation of the plasma cloud near the target. For some metals (steel, Mo, Ti) the plasma cloud was formed without essential evaporation of the target material if the pressure of gases ( $\text{N}_2$ , He, Ar, Xe) remained above 50-70 atm. In those cases no mechanical damage of the surface was noticed [2,3] since the dense plasma cloud screened the metallic surface from the incident laser radiation. The radiated targets changed their physical properties under the action of the plasma cloud interaction with the metallic surfaces. For example, the steel microhardness was increased by a factor of 2-3 in the nitrogen plasma [2]. It was noted that in the plasma absence the laser radiation action reduced to usual heating of the metallic targets [4]. So the active medium, i.e. plasma, is required to change the surface properties. It is rather difficult to obtain sufficient information about the formation and further development of the laser plasma experimentally because of the high pressure, the low transparency of the plasma and a great many of high-speed processes. Experimental data on the initial stage of the plasma development - the optical breakdown of a cold gas - is especially hard to gain.

This paper is concerned with the kinetics analysis for the nitrogen breakdown by the laser radiation near the molybdenum surface.

## 2. MODEL

A laser beam ( $\lambda = 1,06 \text{ m}\mu\text{m}$ ) is incident to the molybdenum plate. The cold gas is transparent to the laser radiation. The incident flux is partially reflected and some portion of it is absorbed. The surface is heated and the energy of emitted electrons is increased by bremsstrahlung. The breakdown dynamics is determined by elastic, inelastic and superelastic collisions with heavy particles. The mathematical model was based on the following elementary collisional processes:



All these processes are nonequilibrium, therefore the problem may be solved in a three-temperature approximation. The equations of chemical kinetics were supplemented by the energy balance equations for electrons and heavy particles; the vibrational energy of molecules was taken into account. The processes of diffusion and transport processes in the electric field of a spatial charge were also considered. The detailed description of the model was given in [5, 6].

The thermoemission current was estimated by the Richardson formula. The influence of the electric field was taken into account by the equation  $j = A T^2 \exp(-\phi/kT) \exp(\alpha u)$ , where  $\alpha$  is the additional work function due to the spatial charge potential  $u$ . Here  $u$  is determined from the Poisson equation.

The surface temperature was determined as a solution of the heat conductivity equation for a target material. The relations to connect one-side fluxes with their functions were given for the right-hand boundary being about  $100 \mu\mu$  apart from the surface. The method of the numerical calculation was discussed in [7].

### 3. DISCUSSION

Let us consider the basic features of the nitrogen optical breakdown. The typical distributions of the main nitrogen particle concentrations and temperatures are given in Fig. 1 at the time of breakdown  $t_{np} \approx 4.35 \times 10^{-9}$  sec and the pressure 100 atm for  $G = 9 \times 10^9$  w/cm<sup>2</sup>. Here N stands for atoms, N<sub>2</sub> for molecules, N\* and N<sub>2</sub>\* for the electron-excited atoms and molecules, respectively, N<sup>+</sup> and N<sub>2</sub><sup>+</sup> for atomic and molecular ions, N<sub>3</sub><sup>+</sup> and N<sub>4</sub><sup>+</sup> for clusters, N<sub>e</sub> for electrons, and T<sub>e</sub>, T<sub>k</sub> and T<sub>v</sub> for the electron, vibrational and heavy particle temperatures, respectively. The jump in the temperatures T<sub>e</sub> and T<sub>k</sub> is typical of the breakdown zone. The increase of the vibrational temperature up to 4.5 eV leads to near complete dissociation (90%) of nitrogen in this zone; the electron-ion avalanche is effected in the atomic component of nitrogen. The molecular nitrogen breakdown does not occur due to large inelastic losses at high T<sub>e</sub>. The electron temperature rise takes place at the point where the rate of Coulomb collisions  $\nu_{ei} = 3.64 \times 10^{16} \text{ sec}^{-1}$

is comparable with the rate of electron-neutral collisions  $\nu_{en} = \frac{1}{2} G(\xi_p) N$ . The nitrogen breakdown is established conditionally by a maximum in the temperature T<sub>e</sub>, which is equal to 1.8 eV for p = 100 atm. The high-temperature zone propagates towards the laser beam under the action of transport processes. The rise in the temperature T<sub>e</sub> results in the increase of the electron and ion concentrations, N<sub>e</sub> and N<sub>i</sub><sup>+</sup>, at the breakdown time  $N_e \approx N_i^+ \approx 3 \times 10^{19} \text{ cm}^{-3}$ .

The calculations have shown the important role of the molecule vibrational excitation reactions  $N_2 + e \rightarrow N_2^* + e$ , the thermal dissociation  $N_2 + N_2 \rightleftharpoons 2N + N^*$ , the electron excitation of molecules and atoms  $N_2 + e \rightleftharpoons N_2^* + e$ ,  $N + e \rightleftharpoons N^* + e$ , and the ionization of excited particles  $N_2^* + e \rightleftharpoons N_2^+ + 2e$ ,  $N_2 + e \rightleftharpoons N_2^+ + 2e$ . Since the contribution of the associative ionization  $N + N \rightarrow N_2^+ + e$  and the main state neutral ionization is negligible, these reactions are not taken into account in the problems with electron sources. The conversion reactions  $N_i^+ + 2N_2 \rightleftharpoons N_{i+2}^+ + N_2^*$  are also not important at T<sub>v</sub> ≤ 0.2 eV.

For the pressure p = 100 atm the breakdown threshold in the radiation density near the target is  $G = 4 \times 10^8$  w/cm<sup>2</sup>, the distance from the surface to the breakdown zone  $x_{np} \sim 0.4 \mu\text{m}$ , the breakdown time  $t_{np} \sim 4.35 \times 10^{-9}$  sec. The values of G<sub>np</sub> and t<sub>np</sub> suggest that the gas breakdown is initiated by the spike of the laser pulse in experiment [1-3]. The surface temperature reaches 0.45 eV, which is not enough for the evaporation to develop at p = 100 atm.

The distance from the metallic surface to the breakdown zone x<sub>np</sub>, the maximal electron temperature T<sub>e</sub> max and the breakdown time t<sub>np</sub> dependences versus pressure P are shown in Fig. 2 for the same G = 9 × 10<sup>9</sup> w/cm<sup>2</sup>. The minimum on the t<sub>np</sub>(p) curve at p = 100 atm indicates that this pressure creates most favourable conditions for evolution of the gas breakdown. The t<sub>np</sub>(p) curve is qualitatively in good agreement with the G<sub>np</sub>(p) curve obtained in experiment [8], where the radiation density minimum

was observed at  $p = 102$  atm.

The calculations confirm the suggestion that the thermoemission is a possible breakdown mechanism at  $p > 30$  atm. For lower pressures  $p \sim 10$  atm the target material evaporation is important at the near-threshold intensities.

#### REFERENCES

- (1) N.N. Rykalin, A.A. Uglov, M.M. Nizametdinov. DAN SSSR, 218, 330 (1974).
- (2) N.N. Rykalin, A.A. Uglov, M.M. Nizametdinov. ZhETF, 69, 722 (1975).
- (3) A.L. Galiev, L.L. Krapivin, L.I. Mirkin, A.A. Uglov. DAN SSSR, 251, 336 (1980).
- (4) A.A. Uglov, A.L. Galiev. Fizika i khimiya obrabotki materialov, 5, 3 (1980).
- (5) V.I. Mazhukin. Preprint IPM AN SSSR, N 30 (1979).
- (6) V.I. Mazhukin, A.A. Uglov, B.N. Chetverushkin. DAN SSSR, 246, 1338 (1979).
- (7) V.I. Mazhukin, A.A. Uglov, B.N. Chetverushkin. ZhVM i MF, 20, 451 (1980).
- (8) D.H. Gill, A.A. Dougal. Phys.Rev.Lett., 15, 845 (1965).

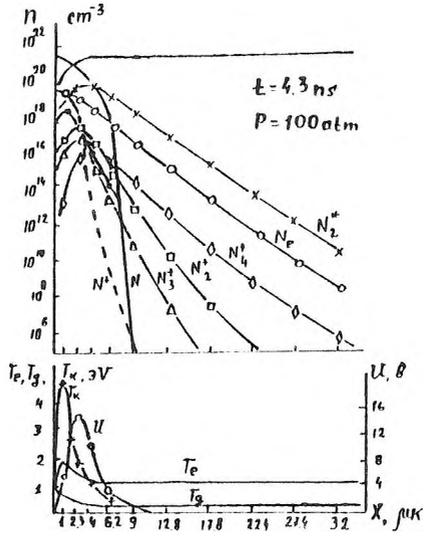


Fig. 1

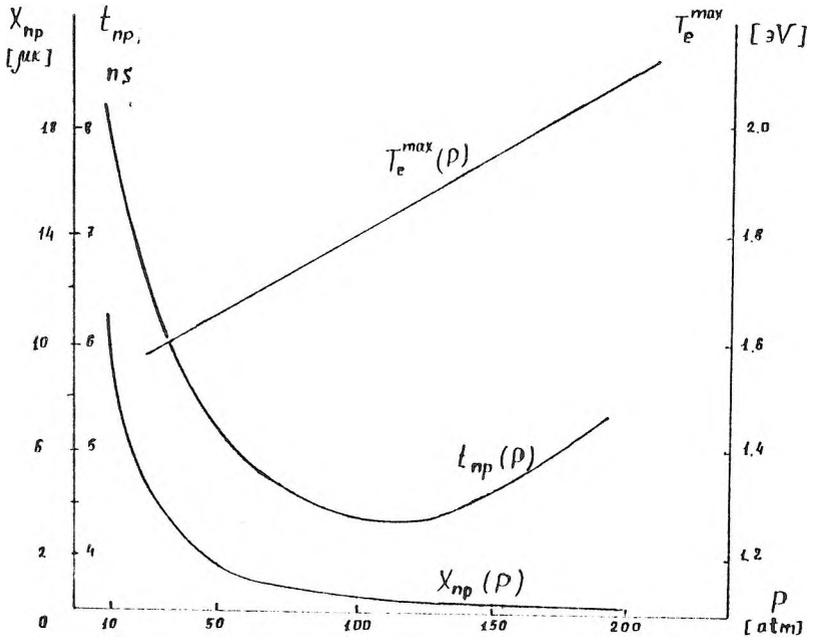


Fig. 2.